



ELSEVIER

Contents lists available at ScienceDirect

American Journal of Infection Control

journal homepage: www.ajicjournal.org

Major Article

Reduction of bacterial burden by copper alloys on high-touch athletic center surfaces

Zina Ibrahim BA, Alexandra J. Petrusan, Patrick Hooke BA, Shannon M. Hinsaleasure PhD *

Department of Biology, Grinnell College, Grinnell, IA

Key Words:

Antimicrobial copper
community-acquired infections
bacterial burden
infection control
built environment

Background: Athletic centers have been locations for the transmission of community-acquired infections. This study assessed the capacity of copper alloys to reduce the bacterial burden associated with high-touch athletic center equipment. Copper alloy weights and grips were rotated with rubber coated and stainless steel controls in an undergraduate college athletic center over a 16-month period. The athletic center is used by college athletic teams, student body, and local community.

Methods: The primary outcome was to compare bacterial burdens on copper and control grips by swabbing surfaces. Significance was determined using the nonparametric Mann-Whitney *U* test with significance assessed at $P < .05$. Secondary outcomes included characterizing bacterial communities on surfaces and conducting antibiotic susceptibility testing using the Kirby-Bauer disk diffusion method.

Results: Control athletic center components carried bacterial loads 94% larger than those found on copper alloy components. Bacterial community characterization revealed *Staphylococcus* to be the most common bacterial genus found on grip surfaces. Antibiotic resistance testing of the *Staphylococcus* isolates revealed that all isolates were susceptible to vancomycin and linezolid, whereas 35% of copper alloy isolates and 44% of control isolates were resistant to erythromycin.

Conclusions: Copper alloys can mitigate the bacterial burden on high-touch surfaces. Strategically placing copper alloys in areas of high human contact can augment infection control efforts and potentially decrease community-acquired infections in athletic centers.

© 2017 Association for Professionals in Infection Control and Epidemiology, Inc. Published by Elsevier Inc. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

According to the World Health Organization, the rise of antibiotic-resistant bacteria is rapidly increasing and eliminating treatment options for infected individuals. Every year in the United States, approximately 2 million people are infected with an antibiotic-resistant pathogen, and at least 23,000 people die as a result of the infection.^{1,2} Early in 2017, the World Health Organization published a priority pathogens list of antibiotic-resistant bacteria on the basis of many factors, some of which included transmissibility and prevention in hospital or community settings.³ Because of the overuse of antibiotics, there is a selective pressure in the environ-

ment for antibiotic resistance genes. The rise of antibiotic-resistant bacteria has led to a greater interest in infection control. Outbreaks of methicillin-resistant *Staphylococcus aureus* (MRSA) infections, primarily hospital-acquired infections, have been found in individuals involved in athletics.⁴ Stanforth et al found that surfaces in high school wrestling facilities tested positive for community-acquired MRSA strains, putting athletes at a higher risk of MRSA infection.⁴ In 2011, there were approximately 80,461 invasive MRSA infections. Of those infections, 60% were hospital-acquired infections, 17.5% were hospital-onset infections, and the remaining 22.5% were community-acquired infections (CAIs). Since 2005, the estimated infection rate for hospital-acquired infections dropped by 27.7%, hospital-onset infections dropped by 54.2%, and CAIs only dropped by 5%.⁵ These findings demonstrate the need for proper hygiene protocols and other approaches to reduce the potential for CAIs in high-touch environments.

Copper and copper alloys are gaining increasing attention in infection control measurements because of their antimicrobial properties. The U.S. Environmental Protection Agency has

* Address correspondence to Shannon M. Hinsaleasure, PhD, Department of Biology, Grinnell College, 1116 8th Ave, Grinnell, IA 50112.

E-mail address: hinsa@grinnell.edu (S.M. Hinsaleasure).

Funding/support: The copper components, control kettlebells, and specialty dumbbells were provided at no cost to Grinnell College through T. Grace of Grace Premier Fitness and Wellness Products Inc, d/b/a Black Iron Strength and GBC Metals LLC, d/b/a Olin Brass.

Conflicts of interest: None to report.

recognized 5 families of copper alloys as antimicrobial, indicating that copper alloys reduce bacterial burdens by 99.9% within 2 hours of exposure.⁶⁻¹² Studies have found that copper surfaces rapidly reduce bacterial loads through a process known as contact killing against both gram-positive and gram-negative bacteria.¹³⁻¹⁷ With the rise of antibiotic-resistant bacteria, such as MRSA, the use of copper alloy surfaces provides a mean of not only reducing bacterial burden, but also mitigating the spread of antibiotic-resistant bacteria in the environment. The implementation of copper alloys on high-touch surfaces in the hospital resulted in decreased bacterial counts on surfaces in comparison with control surfaces.¹⁸⁻²³ Souli et al found copper coating reduced bacterial burden associated high-touch hospital items and lowered the number of surfaces contaminated with multidrug-resistant bacteria.²⁴ The ability of copper to lessen bacterial loads rapidly is important for continuously touched surfaces and therefore can more readily reduce the transmission of antibiotic-resistant bacteria.

In the United States, 57.3 million people are members of at least one athletic facility.²⁵ Athletic facilities are becoming commonly frequented locations, with rates of gym visits expected to increase over the years. With the demonstrated success of copper alloys to significantly reduce bacterial counts in hospital settings, the aim of our study was to determine its efficacy in an athletic center setting and investigate the microbial communities on copper alloys placed on high-touch athletic center equipment. We hypothesized there would be a decrease in bacterial loads on copper alloy surfaces tested compared with bacterial loads found on standard noncopper equipment.

MATERIALS AND METHODS

Study site and cleaning regimen

The study was conducted at the Grinnell College Athletic Center, located in Grinnell, Iowa. The facility is regularly used by college athletic teams, students, faculty and staff of the college, and members of the local community. The cleaning protocol calls for student workers to wipe down machines, benches and bars with GymWipes Antibacterial Wipes (2XL Corporation, Forest Park, IL). Users of the athletic center are also encouraged to wipe down equipment with the GymWipes after their workout. The athletic center is cleaned every morning with Super HDQ L 10 (Spartan Chemical, Maumee, OH). Weights are not cleaned, and only attachments on equipment are wiped.

Study design and sample collection

This trial was designed to determine the bacterial burden on high-touch copper alloy and control athletic equipment over the course of 16 months in a college athletic center and characterize the most common bacteria found on the equipment. Five types of commonly used equipment and attachments made with copper alloy or control grips were tested, including dumbbells (sets at 6.8, 9.1, 11.3, 13.6, and 15.9 kg), barbells (13.6, 18.1, and 22.7 kg), kettlebells (6.8, 11.3, and 15.9 kg), specialty dumbbells (Triple Threat, 6.8 and 9.1 kg), grip attachments, lat pulldown attachments, and low row attachments. The grip areas of the copper alloy equipment were made from C706 copper alloy (90% copper, 10% nickel by weight), whereas the control equipment was rubber coated or exposed stainless steel. The copper alloy equipment and control equipment were rotated in the facility approximately every 3 weeks, and samples were collected 3 times per week. For the kettlebells, barbells, and Triple Threats (Black Iron Strength, Vancouver, WA), only the copper alloy equipment or control was available during the testing time. For the grips and dumbbells, copper alloy pieces were switched with controls; however, other control grips or weights were available, whereas

copper alloy equipment was out because of the demand for >1 grip or set of weights.

Sampling was conducted as previously described by Attaway et al, with the following modification: 4- × 1-in Kimtech W5 wipes (Kimberly-Clark, Roswell, GA) premoistened with 400 µL of phosphate-buffered saline with 0.5% Tween 80 and 0.07% lecithin (PBS-LT) were used to allow for sampling around the grip.²⁶ Wipe samples were collected during open times at the athletic center or directly after it closed after morning hours during the summer. After sampling, each wipe was placed into 6 mL of PBS-LT buffer. Samples were vortexed, diluted with PBS-LT buffer, and plated onto trypticase soy agar with 5% sheep blood (TSAB; BD, Sparks, MD), with incubation for 48 hours at 37°C.

Bacterial characterization and antimicrobial susceptibility test

The most common bacterial morphologies on each plate were selected for identification. Bacterial DNA was isolated and 16S ribosomal RNA amplified as previously described.²⁷ Samples were sequenced at the University of Chicago Comprehensive Cancer Center DNA Sequencing and Genotyping Facility. Sequences were run through DECIPHER²⁸ to check for chimeras and Classifier (Ribosomal Database Project)²⁹ to assign genus. Sequences were deposited in GenBank (accession no. MF385203- MF385271 for copper alloy isolates and MF375118-MF375202 for isolates from control surfaces).

Antimicrobial susceptibility testing was carried out on *Staphylococcus* isolates following published protocols.³⁰ Bacteria were grown on Mueller-Hinton plates (BD) and tested against erythromycin (15 µg), vancomycin (30 µg), and linezolid (30 µg) (BD).

MRSA prevalence

A total of 99 samples were collected during the study, with 49 samples from copper-alloy equipment and 50 samples from control equipment. Samples were collected in the same manner as the bacterial burden protocol, and then plated on CHROMagar MRSAII (BD) following the manufacturer's instructions.

Statistical analysis

For each item, surface areas of sampled regions were measured and the colony forming units (CFU) per 100 cm² were calculated. Bacterial loads on copper alloy items versus noncopper items using nonparametric Mann-Whitney *U* test with a significance level at *P* < .05 using Prism 6 software (GraphPad Software, La Jolla, CA) were calculated.

RESULTS

Bacterial burden was significantly decreased on high-touch copper alloy surfaces compared with controls

Copper grips had significantly lower bacterial loads than control items, with an average decrease of 94% (*n* = 543 for copper and *n* = 536 for control). For every type of grip tested, reductions in bacterial counts decreased from 85%-97% on copper alloy surfaces (Table 1). Control dumbbells carried the highest bacterial loads, with kettlebells and specialty dumbbells carrying the lowest. The highest bacterial loads were found on barbells and specialty dumbbells for the copper alloy grips tested (Table 1). Control 15-lb dumbbells carried the highest bacteria counts with an average of 15,985 CFU/100 cm² (*n* = 34), whereas 40-lb barbells and 35-lb kettlebells carried the lowest (3,311 and 2,923 CFU/100 cm², respectively; *n* = 27 for barbell and *n* = 40 for kettlebell) (Fig 1). Copper grips had the highest bacterial counts on the 30-lb barbell with an average of 724 CFU/

Table 1
Bacterial burdens on equipment and attachment grips

| Type of equipment | Copper components | | | Control components | | | P value | % reduction |
|---------------------|------------------------------|--------------------------------|-----|------------------------------|--------------------------------|-----|---------|-------------|
| | Mean CFU/100 cm ² | Median CFU/100 cm ² | n | Mean CFU/100 cm ² | Median CFU/100 cm ² | n | | |
| Attachment | 416 | 184 | 96 | 6,514 | 3,429 | 103 | <.0001 | 94 |
| Barbell | 535 | 350 | 81 | 6,723 | 2,971 | 81 | <.0001 | 92 |
| Dumbbell | 288 | 141 | 148 | 10,360 | 5,333 | 153 | <.0001 | 97 |
| Kettlebell | 461 | 207 | 137 | 3,722 | 2,182 | 119 | <.0001 | 88 |
| Specialty dumbbells | 551 | 331 | 81 | 3,777 | 2,524 | 80 | <.0001 | 85 |

CFU, colony forming units.

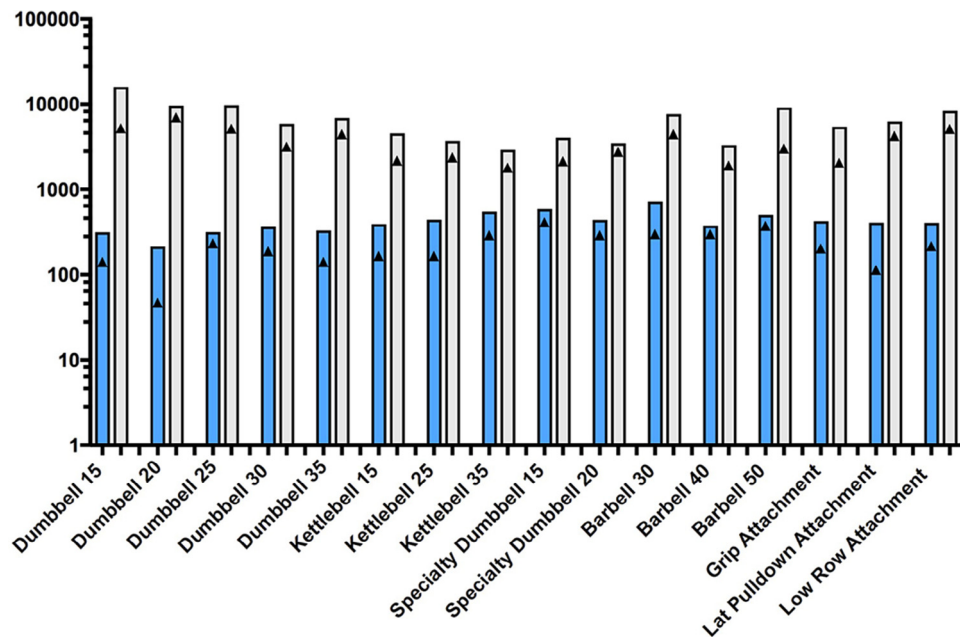


Fig 1. Copper alloy equipment reduced concentrations of bacteria on all equipment types. The mean bacterial concentrations recovered are shown by the bars, whereas the median concentrations are identified by the triangles. Copper alloy grips are represented by the blue bars and controls by the gray bars ($P < .0001$ for all pairs) (numbers range from 25-45 for individual items tested).

100 cm² ($n = 27$), whereas the lowest average was found on 20-lb dumbbells at 215 CFU/100 cm² ($n = 33$).

Characterization of the most common isolates found Staphylococcus dominant in this setting and isolates showed low levels of resistance to 3 antibiotics tests

Staphylococcus and *Micrococcus* were the 2 most prevalent bacterial genera found on both copper alloy and control grips, making up a combined 90% and 91%, respectively, of isolates characterized (Fig 2). Because *Staphylococcus* was most common genus of bacteria found on both types of surfaces, antibiotic susceptibility testing with vancomycin, erythromycin, and linezolid was conducted on 17 isolates from copper surfaces and 18 isolates from control surfaces. All isolates tested were sensitive to vancomycin and linezolid. Erythromycin resistance was found in 6 copper isolates (35%) and 8 control isolates (44%). Of the 99 samples tested for MRSA on CHROMagar MRSAII, no positive MRSA colonies were obtained.

DISCUSSION

In the United States, CAIs have persisted; therefore, maintaining cleanliness and hygiene in locations with high-touch surfaces, such as athletic centers, is important for reducing infection risks.

This study examined the ability of copper alloys to facilitate in hygiene maintenance by controlling bacterial burden on athletic equipment grips. Our findings suggest that U.S. Environmental Protection Agency-registered copper alloys are able to reduce bacterial burdens by 94%, confirming previous observations on the antimicrobial properties of copper.^{18,31,32}

Assessing the bacterial burden on equipment surfaces allows athletic centers to determine which pieces of equipment afford more attention in hygiene maintenance. Across all sampled equipment, the average concentration of bacteria recovered from surfaces was highest for control dumbbells, with a mean concentration of 10,360 CFU/100 cm² (Table 1). Dumbbells had the largest reduction in bacterial burden (97%), whereas specialty dumbbells showed the smallest reduction (85%). Nonetheless, for all equipment groups, copper alloy surfaces had significantly lower bacterial concentrations than control counterparts (Table 1). Although gym users are encouraged to disinfect equipment before and after usage, there is no guarantee that surfaces are being cleaned; therefore, equipment surfaces could go long periods of time without proper disinfection, harboring considerable loads of bacteria. The sustained antimicrobial properties of copper prove useful for continuous hygiene maintenance in locations that may not be regularly disinfected.

Our study also delineated the most common bacterial isolate morphologies associated with copper and control equipment surfaces.

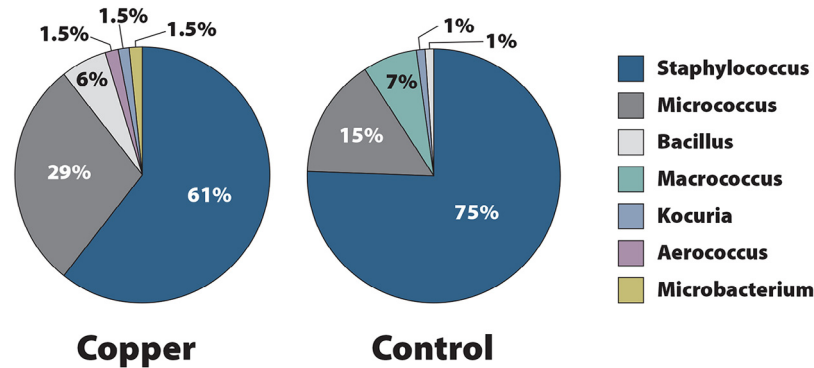


Fig 2. Characterization of the most common colony morphologies present on copper alloy and control surfaces. The most common morphologies from plates were isolated and the 16S ribosomal RNA genes were amplified and sequenced to determine the bacterial identify (n = 69 for copper and n = 89 for control).

The most common bacterial genus was found to be *Staphylococcus*. These findings support previous studies that have identified *Staphylococcus* as one of the most common bacteria found in indoor environments.³³⁻³⁵ Bacteria from microbial communities of the built environment are associated with human skin, outdoor air, and soil microbiomes.³⁶⁻³⁸ Investigating the bacterial diversity associated with gym equipment surfaces, Mukherjee et al determined the presence of *Staphylococcus*, with *Staphylococcus saprophyticus* being the most prevalent species, followed by *Staphylococcus epidermidis* and *S aureus*.³⁵ Each of these bacterial species can exhibit as opportunistic pathogens for humans³⁹⁻⁴² and can therefore pose a threat to individuals who frequent athletic facilities.

Because of the high prevalence of *Staphylococcus* and the risk of infection implicated to antibiotic-resistant species of *Staphylococcus*, antibiotic resistance susceptibility tests were conducted on a selection of *Staphylococcus* isolates collected. Resistance was only present against erythromycin. *Staphylococcus* spp have developed efficient mechanisms to evade the immune system and resist common antibiotics, such as penicillin, cefoxitin, and gentamicin.⁴³ The misuse of antibiotics at subinhibitory levels has been shown to promote bacterial colonization by stimulating enhanced biofilm formation.⁴⁴ The ability of *S aureus* to rapidly develop resistance to antibiotics presents a growing public health problem.⁴⁵ Antimicrobial copper has proved effective in killing pathogenic MRSA.^{46,47} The use of copper could be a suitable solution to the rapid increase of antibiotic-resistant bacteria.

Community-associated MRSA has become a major concern for athletic facilities. Although extensive research on MRSA in hospital settings is available, there is a dearth of studies investigating the prevalence of MRSA on equipment surfaces in athletic facilities. Several reports of MRSA outbreaks in team sports and their training facilities highlight the importance of determining MRSA reservoirs in these environments and implementing cleaning protocols that most efficiently minimize risks of CAI.^{4,48-51} Our study assessed the prevalence of MRSA in our testing site to determine if equipment surfaces could be a source of surface-to-skin contamination. We found no positive cultures of MRSA from either copper alloy or control equipment surfaces. Ryan et al found similar results, with no cultures positive for MRSA from 240 samples obtained from 5 gym surfaces.⁵² Although our findings suggest that athletic centers may not be sources of community-acquired MRSA, our limited sample size of 99 cultures could be insufficient to capture the prevalence of MRSA colonization. Stiefel et al found that hospital surfaces, such as bed rails, bedside tables, and call buttons, served as vectors of surface-to-skin contamination of MRSA for both health care providers and patients.⁵³ These findings suggest that contamination of high-touch environmental surfaces could be sources of infection.

Niiyama et al determined there to be significantly lower MRSA counts on bedsheets with metallic copper imbedded in them, preventing the spread of MRSA in dermatology wards.⁵⁴ Implementation of infection control strategies, such as the use of copper alloys in combination with disinfecting procedures, should be considered to augment cleaning protocols and mitigate the spread of CAIs.

Acknowledgments

We thank Grinnell College and the staff at the Bear Athletic Center for providing assistance and support over the course of this study, especially J. Martinez. We also thank T. Linden, E. Lopatto, H. O'Neill, and K. Vorhies for helpful discussions and assistance with the manuscript.

References

1. Frieden T. Antibiotic resistance threats in the United States. 2013. Available from: <https://www.cdc.gov/drugresistance/threat-report-2013/>. Accessed September 22, 2017.
2. Magill SS, Edwards JR, Bamberg W, Beldavs ZG, Dumyati G, Kainer MA, et al. Multistate point-prevalence survey of health care-associated infections. *N Engl J Med* 2014;370:1198-208.
3. Tacconelli E, Magrini N. Global priority list of antibiotic-resistant bacteria to guide research, discovery, and development of new antibiotics. 2017. Available from: <http://www.who.int/medicines/publications/global-priority-list-antibiotic-resistant-bacteria/en/>. Accessed September 22, 2017.
4. Stanforth B, Krause A, Starkey C, Ryan TJ. Prevalence of community-associated methicillin-resistant *Staphylococcus aureus* in high school wrestling environments. *J Environ Health* 2010;72:12-6.
5. Dantes R, Mu Y, Bellflower R, Aragon D, Dumyati G, Harrison LH, et al. National burden of invasive methicillin-resistant *Staphylococcus aureus* infections, United States, 2011. *JAMA Intern Med* 2013;173:1970-8.
6. United States Environmental Protection Agency. EPA registers copper-containing alloy products. 2008. Available from: <http://www.trimcohardware.com/wp-content/uploads/2015/07/EPA-Copper-Registration.pdf>. Accessed September 22, 2017.
7. United States Environmental Protection Agency. Antimicrobial copper alloys—group I (EPA Reg. No. 82012-1). 2008. Available from: https://www3.epa.gov/pesticides/chem_search/ppls/082012-00001-20140826.pdf. Accessed September 22, 2017.
8. United States Environmental Protection Agency. Antimicrobial copper alloys—group II (EPA Reg. No. 82012-2). 2008. Available from: https://www3.epa.gov/pesticides/chem_search/ppls/082012-00002-20140826.pdf. Accessed September 22, 2017.
9. United States Environmental Protection Agency. Antimicrobial copper alloys—group III (EPA Reg. No. 82012-3). 2008. Available from: https://www3.epa.gov/pesticides/chem_search/ppls/082012-00003-20140826.pdf. Accessed September 22, 2017.
10. United States Environmental Protection Agency. Antimicrobial copper alloys—group IV (EPA Reg. No. 82012-4). 2008. Available from: https://www3.epa.gov/pesticides/chem_search/ppls/082012-00004-20140826.pdf. Accessed September 22, 2017.
11. United States Environmental Protection Agency. Antimicrobial copper alloys—group V (EPA Reg. No. 82012-5). 2008. Available from: https://www3.epa.gov/pesticides/chem_search/ppls/082012-00005-20140826.pdf. Accessed September 22, 2017.

- www3.epa.gov/pesticides/chem_search/ppls/082012-00005-20080229.pdf. Accessed September 22, 2017.
12. United States Environmental Protection Agency. Antimicrobial copper alloys—group VI (EPA Reg. No. 82012-6). 2008. Available from: https://www3.epa.gov/pesticides/chem_search/ppls/082012-00006-20090712.pdf. Accessed September 22, 2017.
 13. Grass G, Rensing C, Solioz M. Metallic copper as an antimicrobial surface. *Appl Environ Microbiol* 2011;77:1541-7.
 14. Santo CE, Quaranta D, Grass G. Antimicrobial metallic copper surfaces kill *Staphylococcus haemolyticus* via membrane damage. *Microbiologyopen* 2012;1:46-52.
 15. Warnes SL, Caves V, Keevil CW. Mechanism of copper surface toxicity in *Escherichia coli* O157:H7 and *Salmonella* involves immediate membrane depolarization followed by slower rate of DNA destruction which differs from that observed for gram-positive bacteria. *Environ Microbiol* 2012;14:1730-43.
 16. Warnes SL, Keevil CW. Mechanism of copper surface toxicity in vancomycin-resistant enterococci following wet or dry surface contact. *Appl Environ Microbiol* 2011;77:6049-59.
 17. Warnes SL, Keevil CW. Lack of involvement of fenton chemistry in death of methicillin-resistant and methicillin-sensitive strains of *Staphylococcus aureus* and destruction of their genomes on wet or dry copper alloy surfaces. *Appl Environ Microbiol* 2016;82:2132-6.
 18. Hinsla-Leasure SM, Nartey Q, Vaverka J, Schmidt MG. Copper alloy surfaces sustain terminal cleaning levels in a rural hospital. *Am J Infect Control* 2016;44:e195-203.
 19. Salgado CD, Sepkowitz KA, John JF, Cantej JR, Attaway HH, Freeman KD, et al. Copper surfaces reduce the rate of healthcare-acquired infections in the intensive care unit. *Infect Control Hosp Epidemiol* 2013;34:479-86.
 20. Schmidt MG, Attaway HH, Sharpe PA, John J Jr, Sepkowitz KA, Morgan A, et al. Sustained reduction of microbial burden on common hospital surfaces through introduction of copper. *J Clin Microbiol* 2012;50:2217-23.
 21. Schmidt MG, Attaway HH, Fahey SE, Steed LL, Michels HT, Salgado CD. Copper continuously limits the concentration of bacteria resident on bed rails within the intensive care unit. *Infect Control Hosp Epidemiol* 2013;34:530-3.
 22. Schmidt MG, von Dessauer B, Benavente C, Benadof D, Cifuentes P, Elgueta A, et al. Copper surfaces are associated with significantly lower concentrations of bacteria on selected surfaces within a pediatric intensive care unit. *Am J Infect Control* 2016;44:203-9.
 23. von Dessauer B, Navarrete MS, Benadof D, Benavente C, Schmidt MG. Potential effectiveness of copper surfaces in reducing health care-associated infection rates in a pediatric intensive and intermediate care unit: a nonrandomized controlled trial. *Am J Infect Control* 2016;44:e133-9.
 24. Souli M, Antoniadou A, Katsarolis I, Mavrou I, Paramythiotou E, Papadomichelakis E, et al. Reduction of environmental contamination with multidrug-resistant bacteria by copper-alloy coating of surfaces in a highly endemic setting. *Infect Control Hosp Epidemiol* 2017;38:765-71.
 25. iHRSA. Health club industry overview. 2016. Available from: <http://www.ihrsa.org/about-the-industry/>. Accessed September 22, 2017.
 26. Attaway HH 3rd, Fahey S, Steed LL, Salgado CD, Michels HT, Schmidt MG. Intrinsic bacterial burden associated with intensive care unit hospital beds: effects of disinfection on population recovery and mitigation of potential infection risk. *Am J Infect Control* 2012;40:907-12.
 27. Hinsla-Leasure SM, Bhavaraju L, Rodrigues JL, Bakermans C, Gilichinsky DA, Tiedje JM. Characterization of a bacterial community from a Northeast Siberian seacoast permafrost sample. *FEMS Microbiol Ecol* 2010;74:103-13.
 28. Wright ES, Yilmaz LS, Noguera DR. DECIPHER, a search-based approach to chimera identification for 16S rRNA sequences. *Appl Environ Microbiol* 2012;78:717-25.
 29. Wang Q, Garrity GM, Tiedje JM, Cole JR. Naive Bayesian classifier for rapid assignment of rRNA sequences into the new bacterial taxonomy. *Appl Environ Microbiol* 2007;73:5261-7.
 30. Cockerill FR, Patel JB, Alder J, Bradford PA, Dudley MN, Eliopoulos GM, et al. Performance standards for antimicrobial susceptibility testing; twenty-third informational supplement. Wayne (PA): Clinical and Laboratories Standards Institute; 2013.
 31. Inkinen J, Makinen R, Keinänen-Toivola MM, Nordstrom K, Ahonen M. Copper as an antibacterial material in different facilities. *Lett Appl Microbiol* 2017;64:19-26.
 32. Schmidt MG, Tuuri RE, Dharsee A, Attaway HH, Fahey SE, Borg KT, et al. Antimicrobial copper alloys decreased bacteria on stethoscope surfaces. *Am J Infect Control* 2017;45:642-7.
 33. Gorny RL, Dutkiewicz J. Bacterial and fungal aerosols in indoor environment in Central and Eastern European countries. *Ann Agric Environ Med* 2002;9:17-23.
 34. Gorny RL, Dutkiewicz J, Krysinska-Traczyk E. Size distribution of bacterial and fungal bioaerosols in indoor air. *Ann Agric Environ Med* 1999;6:105-13.
 35. Mukherjee N, Dowd SE, Wise A, Kedia S, Vohra V, Banerjee P. Diversity of bacterial communities of fitness center surfaces in a U.S. metropolitan area. *Int J Environ Res Public Health* 2014;11:12544-61.
 36. Adams RI, Bateman AC, Bik HM, Meadow JF. Microbiota of the indoor environment: a meta-analysis. *Microbiome* 2015;3:49.
 37. Adams RI, Bhangar S, Pasut W, Arens EA, Taylor JW, Lindow SE, et al. Chamber bioaerosol study: outdoor air and human occupants as sources of indoor airborne microbes. *PLoS ONE* 2015;10:e0128022.
 38. Kembel SW, Jones E, Kline J, Northcutt D, Stenson J, Womack AM, et al. Architectural design influences the diversity and structure of the built environment microbiome. *ISME J* 2012;6:1469-79.
 39. Dong Y, Speer CP. The role of *Staphylococcus epidermidis* in neonatal sepsis: guarding angel or pathogenic devil? *Int J Med Microbiol* 2014;304:513-20.
 40. Kuroda M, Yamashita A, Hiraoka H, Kumano M, Morikawa K, Higashide M, et al. Whole genome sequence of *Staphylococcus saprophyticus* reveals the pathogenesis of uncomplicated urinary tract infection. *Proc Natl Acad Sci USA* 2005;102:13272-7.
 41. Loes AN, Ruyle L, Arvizu M, Gresko KE, Wilson AL, Deutch CE. Inhibition of urease activity in the urinary tract pathogen *Staphylococcus saprophyticus*. *Lett Appl Microbiol* 2014;58:31-41.
 42. Powers ME, Bubeck Wardenburg J. Igniting the fire: *Staphylococcus aureus* virulence factors in the pathogenesis of sepsis. *PLoS Pathog* 2014;10:e1003871.
 43. Nanoukon C, Argemi X, Sogbo F, Orekan J, Keller D, Affolabi D, et al. Pathogenic features of clinically significant coagulase-negative staphylococci in hospital and community infections in Benin. *Int J Med Microbiol* 2017;307:75-82.
 44. Goneau LW, Hannan TJ, MacPhee RA, Schwartz DJ, Macklaim JM, Gloor GB, et al. Subinhibitory antibiotic therapy alters recurrent urinary tract infection pathogenesis through modulation of bacterial virulence and host immunity. *MBio* 2015;6:1-13.
 45. Foster TJ. Antibiotic resistance in *Staphylococcus aureus*. Current status and future prospects. *FEMS Microbiol Rev* 2017;41:430-49.
 46. Noyce JO, Michels H, Keevil CW. Potential use of copper surfaces to reduce survival of epidemic methicillin-resistant *Staphylococcus aureus* in the healthcare environment. *J Hosp Infect* 2006;63:289-97.
 47. Weaver L, Noyce JO, Michels HT, Keevil CW. Potential action of copper surfaces on methicillin-resistant *Staphylococcus aureus*. *J Appl Microbiol* 2010;109:2200-5.
 48. Cohen PR. The skin in the gym: a comprehensive review of the cutaneous manifestations of community-acquired methicillin-resistant *Staphylococcus aureus* infection in athletes. *Clin Dermatol* 2008;26:16-26.
 49. Lindenmayer JM, Schoenfeld S, O'Grady R, Carney JK. Methicillin-resistant *Staphylococcus aureus* in a high school wrestling team and the surrounding community. *Arch Intern Med* 1998;158:895-9.
 50. Montgomery K, Ryan TJ, Krause A, Starkey C. Assessment of athletic health care facility surfaces for MRSA in the secondary school setting. *J Environ Health* 2010;72:8-11, quiz 66.
 51. Rackham DM, Ray SM, Franks AS, Bielak KM, Pinn TM. Community-associated methicillin-resistant *Staphylococcus aureus* nasal carriage in a college student athlete population. *Clin J Sport Med* 2010;20:185-8.
 52. Ryan KA, Infantes C, Bucciarelli C, Saliba H, Tuli S, Black E, et al. Are gymnasium equipment surfaces a source of staphylococcal infections in the community? *Am J Infect Control* 2011;39:148-50.
 53. Stiefel U, Cadnum JL, Eckstein BC, Guerrero DM, Tima MA, Donskey CJ. Contamination of hands with methicillin-resistant *Staphylococcus aureus* after contact with environmental surfaces and after contact with the skin of colonized patients. *Infect Control Hosp Epidemiol* 2011;32:185-7.
 54. Niiyama N, Sasahara T, Mase H, Abe M, Saito H, Katsuoaka K. Use of copper alloy for preventing transmission of methicillin-resistant *Staphylococcus aureus* contamination in the dermatology ward. *Acta Derm Venereol* 2013;93:294-300.